

ALPHA[®] CVP-520

Low Melting Point, No-Clean, Lead-Free Zero Halogen Solder Paste

DESCRIPTION

ALPHA CVP-520 is designed to enable low temperature surface mount assembly technology. The lead-free alloy in **ALPHA CVP-520** has a melting point below 140 °C, and has been successfully used with peak reflow profiles between 155 °C and 190 °C. The flux residue from **ALPHA CVP-520** is clear, colorless, and provides excellent electrical resistivity, exceeding industry standards.

This product enables the elimination of an extra wave or selective wave soldering process when temperature sensitive through hole components are used in an assembly. Eliminating a wave soldering or selective soldering step can significantly lower the cost of producing an electronic assembly, increase daily throughput, eliminate the need for managing bar solder and wave soldering flux supplies and eliminate the need for pallets. The carefully selected Sn/Bi/Ag alloy in **ALPHA CVP-520** was selected to give the lowest melting point, lowest pasty range during melting and re-solidification, along with a very fine grain structure, offering maximum resistance to thermal cycle based fatigue. The alloy also yields very low voiding BGA solder joints, even when a traditional SAC alloy sphere is used.

The use of **ALPHA Exactalloy** performs may enable the elimination of selective wave soldering by providing additional solder volume when needed.

All components used with **ALPHA CVP-520** must be lead-free to eliminate the formation of tin/lead/bismuth intermetallic which has a melting point under 100 °C.

READ ENTIRE TECHNICAL DATA SHEET BEFORE USING THIS PRODUCT

FEATURES & BENEFITS

- Enables elimination of a second or third reflow cycle when temperature sensitive components or connectors are used.
- Reduces energy consumption in reflow ovens versus standard lead free alloys.
- Reduces reflow process cycle time.
- Delivers 8 Hour stencil life.
- Potential eliminations of bar solder, wave soldering flux and energy costs associated with wave soldering.
- Compatible with all commonly used lead free surface finishes (Entek HT; Alpha Star Immersion Silver, Immersion Tin, Ni/Au, SACX HASL, etc.)

- Excellent resistance to random solder balling minimizing rework and increasing first time yield.
- Low temperature reflow profiles may enable the use of less expensive printed circuit board substrates, when appropriate.
- Meets highest IPC 7095 voiding performance (Class III).
- Provides excellent electrical reliability properties.
- Zero halogen (no halogen intentionally added) and halide-free material.
- Compatible with either nitrogen or air reflow.

PRODUCT INFORMATION

Formulated for both standard and fine pitch stencil printing, at print speeds of between 40mm/sec (1.5"/sec) and 100mm/sec (4"/sec), with stencil thickness of 0.100mm (0.004") to 0.150mm (0.006"), particularly when used in conjunction with ALPHA Stencils. Blade pressures should be 0.18 to 0.27 kg/cm of blade (1.0 to 1.5 lbs/inch), depending upon the print speed. The higher the print speed employed, the higher the blade pressure that is required to prevent smearing on the stencil. Examples of successful reflow profiles are outlined below. Generally, peak temperatures of 155 to 190 °C have proven effective.

| | |
|-------------------------|--|
| <u>Alloys:</u> | 42%Sn/57.6%Bi/0.4%Ag (Alpha holds the appreciate license to supply this alloy into the United States, UK, Germany and/or Korea, as covered by the following patents (US Patents 5,569,433; Korea Patent 400121; German Patent 69521762.3; Great Britain Patent 0711629) 42%Sn/57%Bi/1.0%Ag, available upon request |
| <u>Powder Size:</u> | Type 3, Type 4, Type 5 |
| <u>Residues:</u> | Approximately 5% by (w/w) |
| <u>Packaging Sizes:</u> | 500gram jars, 6" & 12" cartridges |
| <u>Flux Gel:</u> | CVP-520 Flux Gel is available in 10cc and 30cc syringes for rework applications. |
| <u>Lead Free:</u> | Complies with RoHS Directive 2002/95/EC. |

TECHNICAL DATA

| Category | Results | Procedures/Remarks |
|--|---|---|
| Chemical Properties | | |
| Activity Level | RoI0 = J-Std Classification | IPC J-STD-004 |
| Halide Content | Halide Free (By Titration). Passes Ag Chromate Test | IPC J-STD -004 |
| Halogen Content | Pass, Zero Halogen - No Halogen Intentionally Added | En14582, By Oxygen Bomb Combustion, Non Detectable (Nd) At < 50 Ppm |
| Copper Mirror Test | Pass | IPC J-STD-004 |
| Copper Corrosion Test | Pass, (No Evidence Of Corrosion) | IPC J-STD-004 |
| | Pass, (No Evidence Of Corrosion) | JIS Z 3197 -1999 8.4.1 |
| Electrical Properties | | |
| Sir (Ipc 7 Days @ 85 °C/85%Rh) | Pass | IPC J-STD-004 {Pass = 1 X 10 ⁸ Ohm Min} |
| Sir (Bellcore 96 Hrs@ 5 °C/85%Rh) | Pass | Bellcore Gr78-Core {Pass = 1x10 ¹¹ Ohm Min} |
| Electromigration (Jis Z 3197 @ 85 °C/85%Rh 48v Dc 1000 Hrs) | Final Reading > 10 ¹⁰ Ohms No Migration After 1000 Hrs =Pass | JIS Z 3197 1999 |
| Physical Properties (90-3 M 21 Viscosity - Malcolm Viscometer @10 Rpm, 25 °C) | | |
| Color | Clear, Colorless Flux Residue | |
| Tack Force Vs. Humidity (T = 8 Hours) | Pass - Change Of <1g/Mm ² Over 24 Hours at 25% And 75 % Rh | IPC J-STD-005 |
| | Pass - Change Of <10% When Stored at 25±2 °C And 50±10% Rh | JIS Z 3284 Annex 9 |
| Viscosity | 85.3% Metal Loading Designated M11 For Dispensing. 90% Metal Load Designated M21 For Printing. 86.5% Metal Load, Type 4 Powder Designated M10 For Dispense. Viscosity (Typical) 1000 Poise, 10 Rpm | Malcom Spiral Viscometer; J-STD-005 |
| Solderball | Acceptable | IPC J-STD-005 |
| Stencil Life | >8 Hours | @ 50%Rh, 23 °C (74 °F) |
| Spread | >87% | Jis-Z-3197: 1999 8.3.1.1 |
| Slump | Pass | Modified Ipc J-Std-005 (10 Min 100 °C) |
| | Pass | JIS Z-3284-1994 Annex 8 |

PROCESSING GUIDELINES


| Storage & Handling | Printing | Reflow (See Figure #1) | Cleaning |
|---|--|---|--|
| <p>Refrigerate to guarantee stability at 0 to 10 °C, 32 to 50 °F</p> <p>Shelf life of refrigerated paste is (6) months</p> <p>Paste can be stored for 2 weeks at room temperature up to (25 °C/77 °F) prior to use</p> <p>When refrigerated, allow paste container to warm to room temperature for up to four hours. Paste must be \geq (19 °C/66 °F) before processing. Verify paste temperature with a thermometer to ensure paste is (19 °C/66 °F) or greater before set-up. Printing can be performed at temperatures up to (29 °C/84 °F).</p> <p>These are starting recommendations and all process settings should be reviewed independently.</p> <p>Working conditions: 19 to 29 °C on the stencil.</p> | <p><u>Stencil:</u> Recommended ALPHA CUT or ALPHA FORM stencils @ (0.100 to 0.150 mm), (4 to 6 mil) thick for (0.4 to 0.5mm) (0.016" or 0.020") pitch. Stencil design is subject to many process variables. Contact your local Alpha stencil site for advice.</p> <p><u>Squeegee:</u> Metal (recommended)</p> <p><u>Pressure:</u> (0.18 to 0.27) kg/cm of squeegee length (1.0 to 1.5 lbs/inch).</p> <p><u>Speed:</u> 40 to 100mm per second 1.5 to 4 inches per second.</p> <p><u>Stencil Release Speed:</u> 3 to 10 mm (0.12 to 0.4 inches)/ sec.</p> <p><u>Lift Height:</u> 8 to 14mm (0.31 to 0.55")</p> | <p><u>Atmosphere:</u> Clean-dry air or nitrogen atmosphere.</p> <p><u>Profile:</u> See Figure #1</p> <p>Acceptable reflow / coalescence & IPC Class III voiding were obtained with the given profile</p> <p>Note: Refer to component and board supplier data for thermal preoperties at elevated temperatures. Lower peak temperatures require longer TAL for improved joint cosmetics.</p> | <p>CVP-520 residue is designed to remain on the board after reflow.</p> <p>If reflowed residue cleaning is required, ALPHA BC-2200 aqueous cleaner is recommended.</p> <p>For solvent cleaning, agitation for 5 min in the following cleaners is recommended:</p> <ul style="list-style-type: none"> - ALPHA SM-110E - Bioact SC-10E - Kyzen Micronox MX2501 <p>Misprints and stencil cleaning may be done with:</p> <ul style="list-style-type: none"> - ALPHA SM-110E - ALPHA SM-440 - ALPHA BC-2200 - Bioact™ SC-10E cleaners. |

Bioact is a registered trademark of Petroferm, Inc.

REFLOW PROFILES

| General Reflow Profile Guidelines | |
|-----------------------------------|------------------------|
| Parameter | Guidelines |
| Atmosphere | Air or N2 |
| SnBiAg (42/57.6/0.4)alloy | 138 °C (near eutectic) |
| Setting Zone | Optimal Dwell Perior |
| 40 to 138 °C | 2:10 to 4:00 minutes |
| 125 to 138 °C | 0:30 to 1:30 minutes |
| 100 to 138 °C | 1:15 to 2:00 minutes |
| TAL (138 °C) | 0:30 to 1:30 minutes |
| Peak temperatures | 155 to 180 °C |
| Joint cool down rate from 170 °C | 3 to 8 °C/sec |

Figure #1 – CVP-520 Reflow Profile Envelope

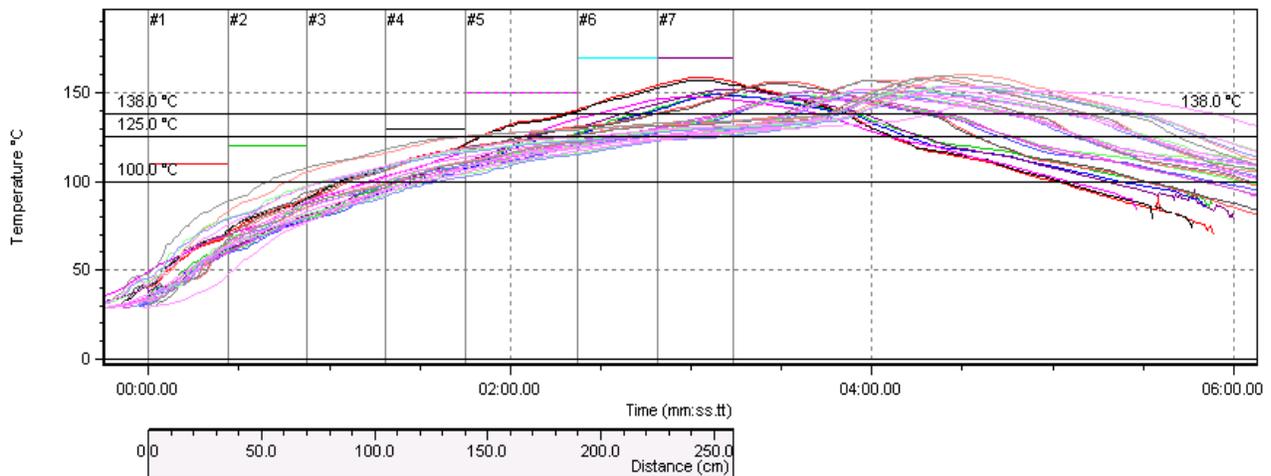

SAFETY & WARNING

It is recommended that the company/operator read and review the Safety Data Sheets for the appropriate health and safety warnings before use. **Safety Data Sheets are available at MacdermidAlpha.com/assembly-solutions/knowledge-base**

STORAGE

ALPHA CVP-520 should be stored in a refrigerator upon receipt at 0 to 10 °C (32 to 50 °F). ALPHA CVP-520 should be permitted to reach room temperature before unsealing its package prior to use (see handling procedures on page 3). This will prevent moisture condensation build up in the solder paste.

CONTACT INFORMATION

To confirm this document is the most recent version, please contact Assembly@MacDermidAlpha.com

www.macdermidalpha.com

| | | |
|--|---|---|
| <p>North America 109 Corporate Blvd. South Plainfield, NJ 07080, USA 800.367.5460</p> | <p>Europe Unit 2, Genesis Business Park Albert Drive Woking, Surrey, GU21 5RW, UK 01483.758400</p> | <p>Asia 8/F., Paul Y. Centre 51 Hung To Road Kwun Tong, Kowloon, Hong Kong 852.3190.3100</p> |
|--|---|---|

Also read carefully warning and safety information on the Safety Data Sheet. This data sheet contains technical information required for safe and economical operation of this product. READ IT THOROUGHLY PRIOR TO PRODUCT USE. Emergency safety directory assistance: US 1 202 464 2554, Europe + 44 1235 239 670, Asia + 65 3158 1074, Brazil 0800 707 7022 and 0800 172 020, Mexico 01800 002 1400 and (55) 5559 1588

DISCLAIMER: All statements, technical information and recommendations contained herein are based on tests we believe to be reliable, but the accuracy or completeness thereof is not guaranteed. No statement or recommendation shall constitute a representation unless set forth in an agreement signed by officers of seller and manufacturer. NO WARRANTY OF MERCHANTABILITY, WARRANTY OF FITNESS FOR A PARTICULAR PURPOSE OR ANY IMPLIED WARRANTY IS MADE. The following warranty is made in lieu of such warranties and all other warranties, express, implied, or statutory. Products are warranted to be free from defects in material and workmanship at the time sold. The sole obligation of seller and manufacturer under this warranty shall be to replace any noncompliant product at the time sold. Under no circumstances shall manufacturer or seller be liable for any loss, damage or expense, direct, indirect, incidental or consequential, arising out of the inability to use the product. Notwithstanding the foregoing, if products are supplied in response to a customer request that specifies operating parameters beyond those stated above, or if products are used under conditions exceeding said parameters, the customer by acceptance or use thereof assumes all risk of product failure and of all direct, indirect, incidental and consequential damages that may result from use of the products under such conditions, and agrees to exonerate, indemnify, defend and hold harmless MacDermid, Incorporated and its affiliates therefrom. No suggestion for product use nor anything contained herein shall be construed as a recommendation to use any product in a manner that infringes any patent or other intellectual property rights, and seller and manufacturer assume no responsibility or liability for any such infringement.

© 2019 MacDermid, Inc. and its group of companies. All rights reserved. "(R)" and "TM" are registered trademarks or trademarks of MacDermid, Inc. and its group of companies in the United States and/or other countries.